arXiv:cond-mat/0412741v2 [cond-mat.dis-nn] 26 May 2005

Frequency dependent effective conductivity of two-dimensional metal-dielectric composites

LOTFI ZEKRI[1]
Institute for Theoretical Physics, Cologne University, D-50923 Köln, Germany
E-mail: zekri@thp.uni-koeln.de

Abstract

We analyze a random resistor-inductor-capacitor (RLC) lattice model of 2 dimensional metal-insulator composites. The results are compared with Bruggeman's and Landauer's Effective Medium Approximations predictions where a discrepancy was observed for some frequency zones. Such a discrepancy is mainly caused by the strong conductivity fluctuations. Indeed, a two-branches distribution is observed for low frequencies. We show also that at p_c the so-called Drude peak vanish by increasing the system size and increase for vanishing losses.

Keywords: conductivity, composites, resistor networks, percolation.

1 Introduction

The optical properties of composite materials are very different from those of their constituents particularly in metal insulator composites [1, 2]. Theses differences are mainly observed at percolation threshold p_c at which one of the two components of the composite first forms a connected path extending through the system [3]. Bruggeman's and Landauer's Effective Medium Aproximation (BEMA [4], LEMA [5]) provides the most useful way to describe these properties.

Zeng et al. [6], following the work of Koss and Stroud [7], analyzed the optical properties of a two-dimensional normal-metal-insulator composite.

They found a surface plasmon resonance peak of the real part of the conductivity for various concentrations above and below p_c in agreement with LEMA. For *dc* case, Watson and Leath [8] gave equation to correct the slope of the curve at the critical concentration. Koss and Stroud generalized this equation to their *ac* problem. The so-called surface plasmon modes are known to be an important absorption mechanism in random metal-insulator composites [9]. Drude peak, corresponding to nonzero dc conductivity at and above p_c was also found. This peak is due at p_c to the finite size effects and is expected by Koss and Stroud to vanish in the limit of infinite systems. For system size 100×100 Zeng chose a characteristic relaxation time value of 10 in RLC systems corresponding to a large loss in the metallic component $R = 10^{-1}$ ($\tau = L/R$). For vanishing losses the local field and the *ac* conductivity fluctuations are strong mainly at percolation threshold p_c [10, 11]. Thus calculations for only 5 samples, as done by Zeng, for vanishing losses, will not be statistically sufficient.

---

[1] Permanent address: *U.S.T.O., Département de Physique, L.E.P.M., B.P.1505 El M'Naouar, Oran, Algeria. Email: lzekri@yahoo.com*

Zeng et al. used Frank and Lobb algorithm [12], for frequencies ranged from 10^{-2} to 1 (expressed in units of the plasmon frequency ω_p). This algorithm is very fast but based on many division operations, which causes a numerical instabilities both for smaller frequencies and losses. In order to compute the effective conductivity for the corresponding $2d$ resistor network for smaller frequencies and losses, we use a method of exactly solving Kirchoff's equations, extensively described in Refs [13]. By using this method the current is preserved in all nodes of the square lattice and the total entering and outgoing currents of the sample are accurately identical.

In this paper we present a numerical study on $2d$ resistor network model for a large frequency range including the plasmon frequency ω_p around the bond percolation threshold p_c for smaller loss and larger size.

Confirming Koss and Stroud prediction we show that the Drude peak decreases by increasing the system size. We show also that for vanishing losses Drude peak increase and, at percolation threshold p_c, for low frequencies the distribution of the real part of the effective conductivity is splitted in two branches, the first one is due to the non percolate samples and the second branch to the percolate ones. The results allow us to test the validity of the above cited BEMA and LEMA.

2 Model description

It is well known that in the optical frequency region a semi-continuous metallic film can be modelled as a $2d$ $RL-C$ lattice [2]. Capacitors C stand for the dielectric grains that have dielectric constant ϵ_d, while the inductance L represents the metallic grains characterized for Drude metal by the following dielectric function [14],

$$\epsilon_m(\omega) = \epsilon_b - (\omega_p/\omega)^2/[1 + i\omega_\tau/\omega] \tag{1}$$

where ϵ_b is the contribution to ϵ_m due to the inter-band transitions, $\omega_\tau = 1/\tau$ is the relaxation rate and ω_p is the plasmon frequency. While for dielectric grains, the dielectric function is,

$$\epsilon_d = cte \tag{2}$$

The metal conductivity $\sigma_m = -i\epsilon_m\omega/4\pi$ is characterized by positive imaginary part in the optical frequency region (inductive behavior) [2]. We can then model the metallic grains as inductances L with loss R ($\sigma_m = (R + iL\omega)^{-1}$) while the dielectric grains can be represented by capacitances C ($\sigma_d = iC\omega$). We can take without loss of generality, $L = C = \omega_p = 1$, (ω_p corresponds to the case where $\mid \sigma_m \mid \simeq \mid \sigma_d \mid$ for vanishing losses, i.e., $C\omega_p = 1/L\omega_p$). The inductance L and the capacitance C can be assumed to be constant in the range between $1/\tau$ and ω_p, we express in this paper the frequency in units of the plasmon frequency ($\tilde{\omega} = \omega/\omega_p < 1$).

We model the metal dielectric composite films as a square lattice composed of metallic bonds with conductivity :

$$\sigma_m = (R + i\tilde{\omega})^{-1} \tag{3}$$

and concentration p, and dielectric bonds with conductivity:

$$\sigma_d = i\tilde{\omega} \tag{4}$$

and concentration $1-p$.

In order to compare with Zeng's results, we model the metal by a capacitance parallel to RL branch, this is called $RL\|C$ model to be distinguished from the RL one.

3 Results and discussion

We consider a lattice of size $n \times n$ ($n = 100$, 200 and 600). If we choose $R = 10^{-3}$, the smaller system size is larger than the correlation length (following Zekri et al. [11], the correlation length behaves as $R^{-1/2}$). We choose then losses R not smaller than the above value so that we ensure a correlation length always smaller than the system size. This avoids the size dependent effects of the conductivity. The effective conductivity here is averaged from 550 samples and compared to Zeng's simulations for only 5 samples.

Let us first reproduce Zeng's results on the effective conductivity by exactly solving Kirchoff laws [13] for an $RL\|C$ model. We compare them to RL model at p_c with $R = 10^{-1}$. In $Figure 1a$, the two models seem to produce identical results except near $\tilde{\omega} = 1$, where the real part of the conductivity seems to vanish for $RL\|C$ model while it saturates for RL model, the divergence between the two models start from the frequency $\tilde{\omega} = 0.35$. Large fluctuations of this conductivity are observed below $\tilde{\omega} = 10^{-2}$. We show also that the two models are in a good agreement with BEMA for all the frequency range investigated and are different from LEMA. Comparison between the two models at p_c with $R = 10^{-3}$ is done for sizes 100 and 200. They produce also identical results but the fluctuations extends to the whole frequency range investigated. Then we have done calculations for large samples using RL model. In $Figure 1b$ comparison between RL model for system sizes 100, 200 and 600 and both BEMA and LEMA is done at p_c with $R = 10^{-3}$. The size effect on Drude peak is also investigated. The results obtained and BEMA are alike only for frequencies ranged from 10^{-2} to 1, and they follow qualitatively LEMA for low frequencies, where Drude peak increase by decreasing the loss. We see also in this figure that Drude peak decreases by increasing the system size and should vanish in the limit of infinite systems as predicted by Koss and Stroud [7]. The data in the described curves are directly averaged (i. e. Arithmetic Average (AA) of the 550 samples for sizes 100 and 200 and 30 samples for the size 600). In order to check the validity of this average, the same results for the size 200 are plotted using Logarithmic Average(LA). The LA curve and the AA one are alike for frequencies ranged from 10^{-2} to 1, and they diverge for low frequencies.

It is then important to investigate the conductivity distributions for frequencies in the range examined here. For $\tilde{\omega} = 1$ the distribution of the real part is Gaussian centered at 1. For $\tilde{\omega} = 10^{-1}$ the distribution becomes broader and at $\tilde{\omega} = 10^{-2}$ it becomes poissonian (the distributions for $\tilde{\omega} = 1$, 10^{-1} and 10^{-2} are not plotted here). In $Figures 2a$ we show for $\tilde{\omega} = 10^{-3}$ that the distribution is splitted in two branches, the first one has the form of a peak centered at the vicinity of zero and the second one has a low height and is broad, its width tends towards large positive values. The two branches distribution observed for frequencies less than 10^{-2} are the reason of the large divergence between AA and LA. In $Figures 2b$ and

$2c$ we compare for the frequency $\tilde{\omega} = 10^{-3}$ the distributions of the real part for concentrations p of the metallic grains (RL bound) below and above p_c. Above p_c means $p - p_c = 1/N^{1/\nu}$ and below p_c, $p - p_c = -1/N^{1/\nu}$ where the connectivity length exponent ν [3] is $4/3$ for $d = 2$ and N is the system size. The peak centered in the vicinity of zero (first branch) increases below p_c and tends to disappear above p_c, whereas the width of the second branch tends to disappear below p_c, and increase above p_c and becomes dominant. Therefore the two branches appear only at p_c. The first branch is related to the non percolate samples and the second branch is related to the percolate ones. Similar behavior of this conductivity distribution has been observed recently [15] for the distribution of the critical links (singly connected links [3, 16]). The disappearance of one branch corresponds to that observed for critical links below p_c (also observed when the system size increase [15]). Such branch corresponds to configurations for which the infinite cluster has a very small number of critical links.

4 Conclusion

In this paper we have compared (RLC) lattice model with BEMA and LEMA at and near the percolation threshold p_c for large and small loss in the metallic component. For large loss the results and BEMA are alike for all the frequency range investigated, but for small loss they are alike only for frequencies ranged from 10^{-2} to 1, and they follow qualitatively Landauer's approximation for lower frequencies. We have also shown that for small loss the arithmetic and the logarithmic average of the real part of the effective conductivity diverge for frequencies less than 10^{-2} due to two branches distribution of the real part of the effective conductivity. The first one is due to non percolate samples and the second branch is due to percolate ones. We showed also in this paper that Drude peak increases by decreasing the metallic loss and vanish with the size as predicted by Stroud [7] at p_c.

Acknowledgments

I wish to thank Professors D.Stauffer and N.Zekri for helpful discussions and DAAD for financial support during the progress of this work.

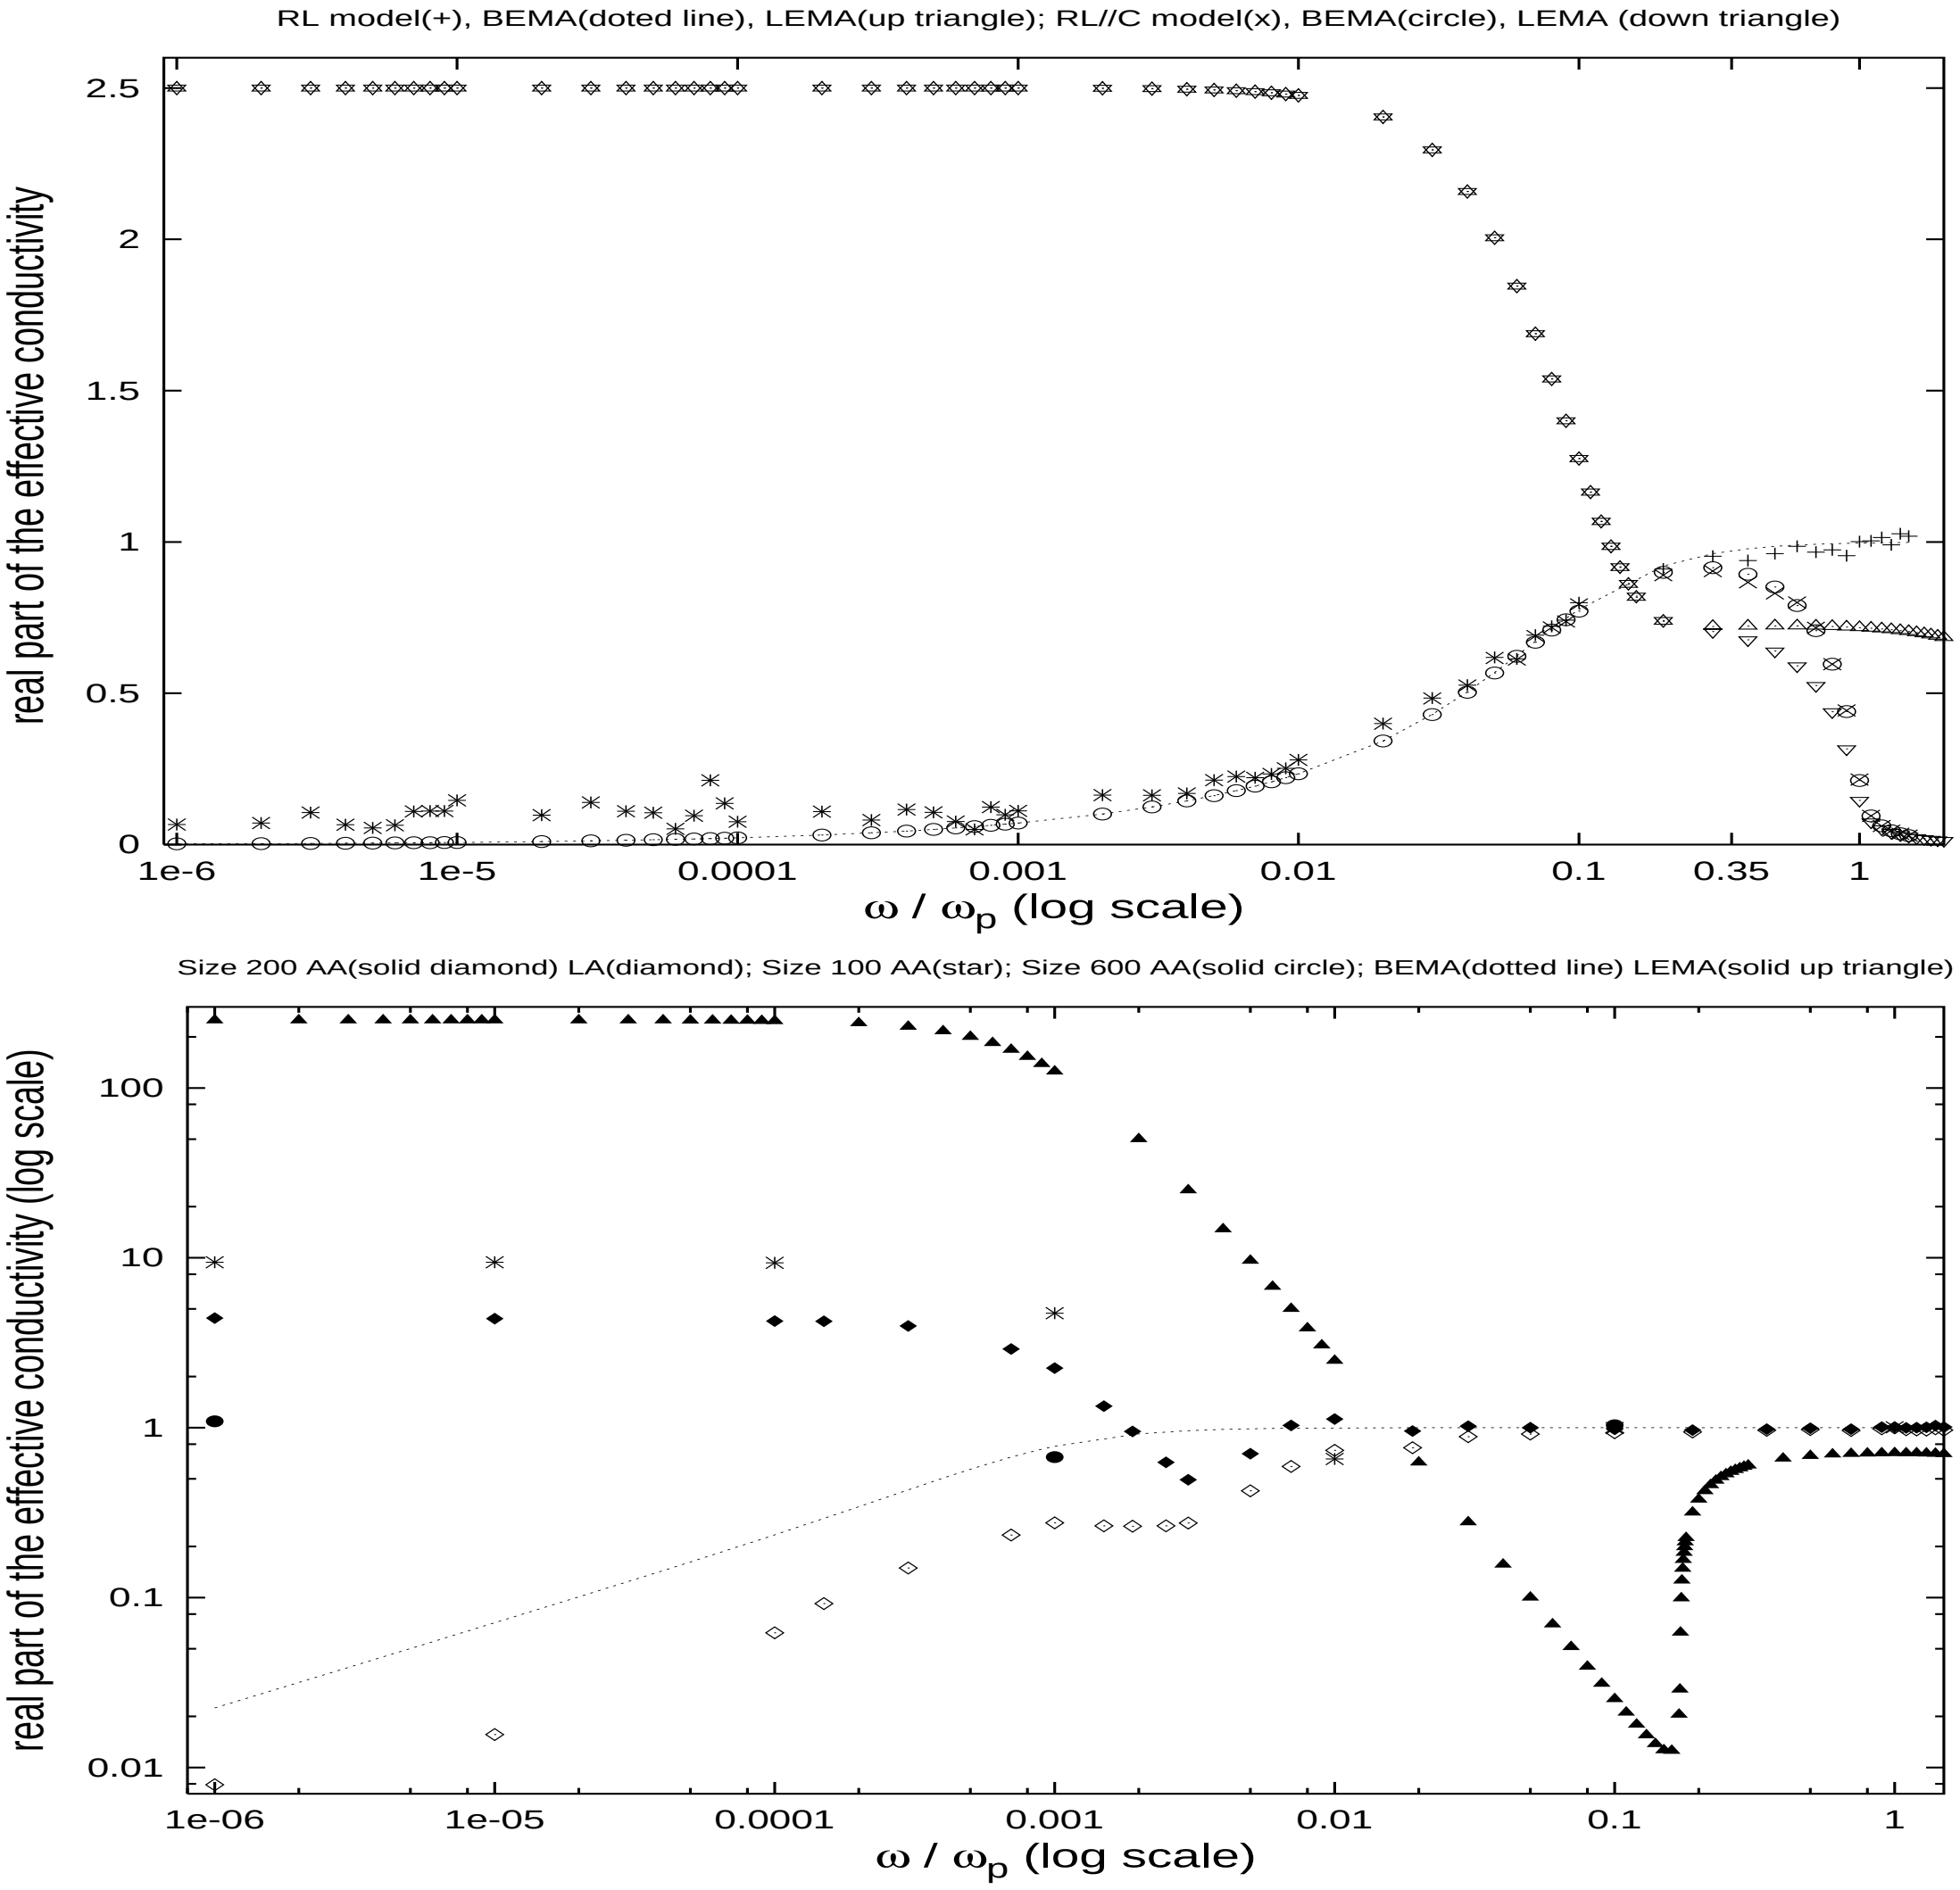

RL model(+), BEMA(doted line), LEMA(up triangle); RL//C model(x), BEMA(circle), LEMA (down triangle)

Size 200 AA(solid diamond) LA(diamond); Size 100 AA(star); Size 600 AA(solid circle); BEMA(dotted line) LEMA(solid up triangle)

Figure 1: *a*) $R = 10^{-1}$, Arithmetic Average (AA) over 5 samples of size 100. *b*) $R = 10^{-3}$, RL model, AA over 550 samples for the sizes 100 and 200 and 30 samples for the size 600. Logarithmic Average(LA) for the size 200. The real part of the effective conductivity is expressed in arbitrary units and the frequency is expressed in units of the plasmon frequency.

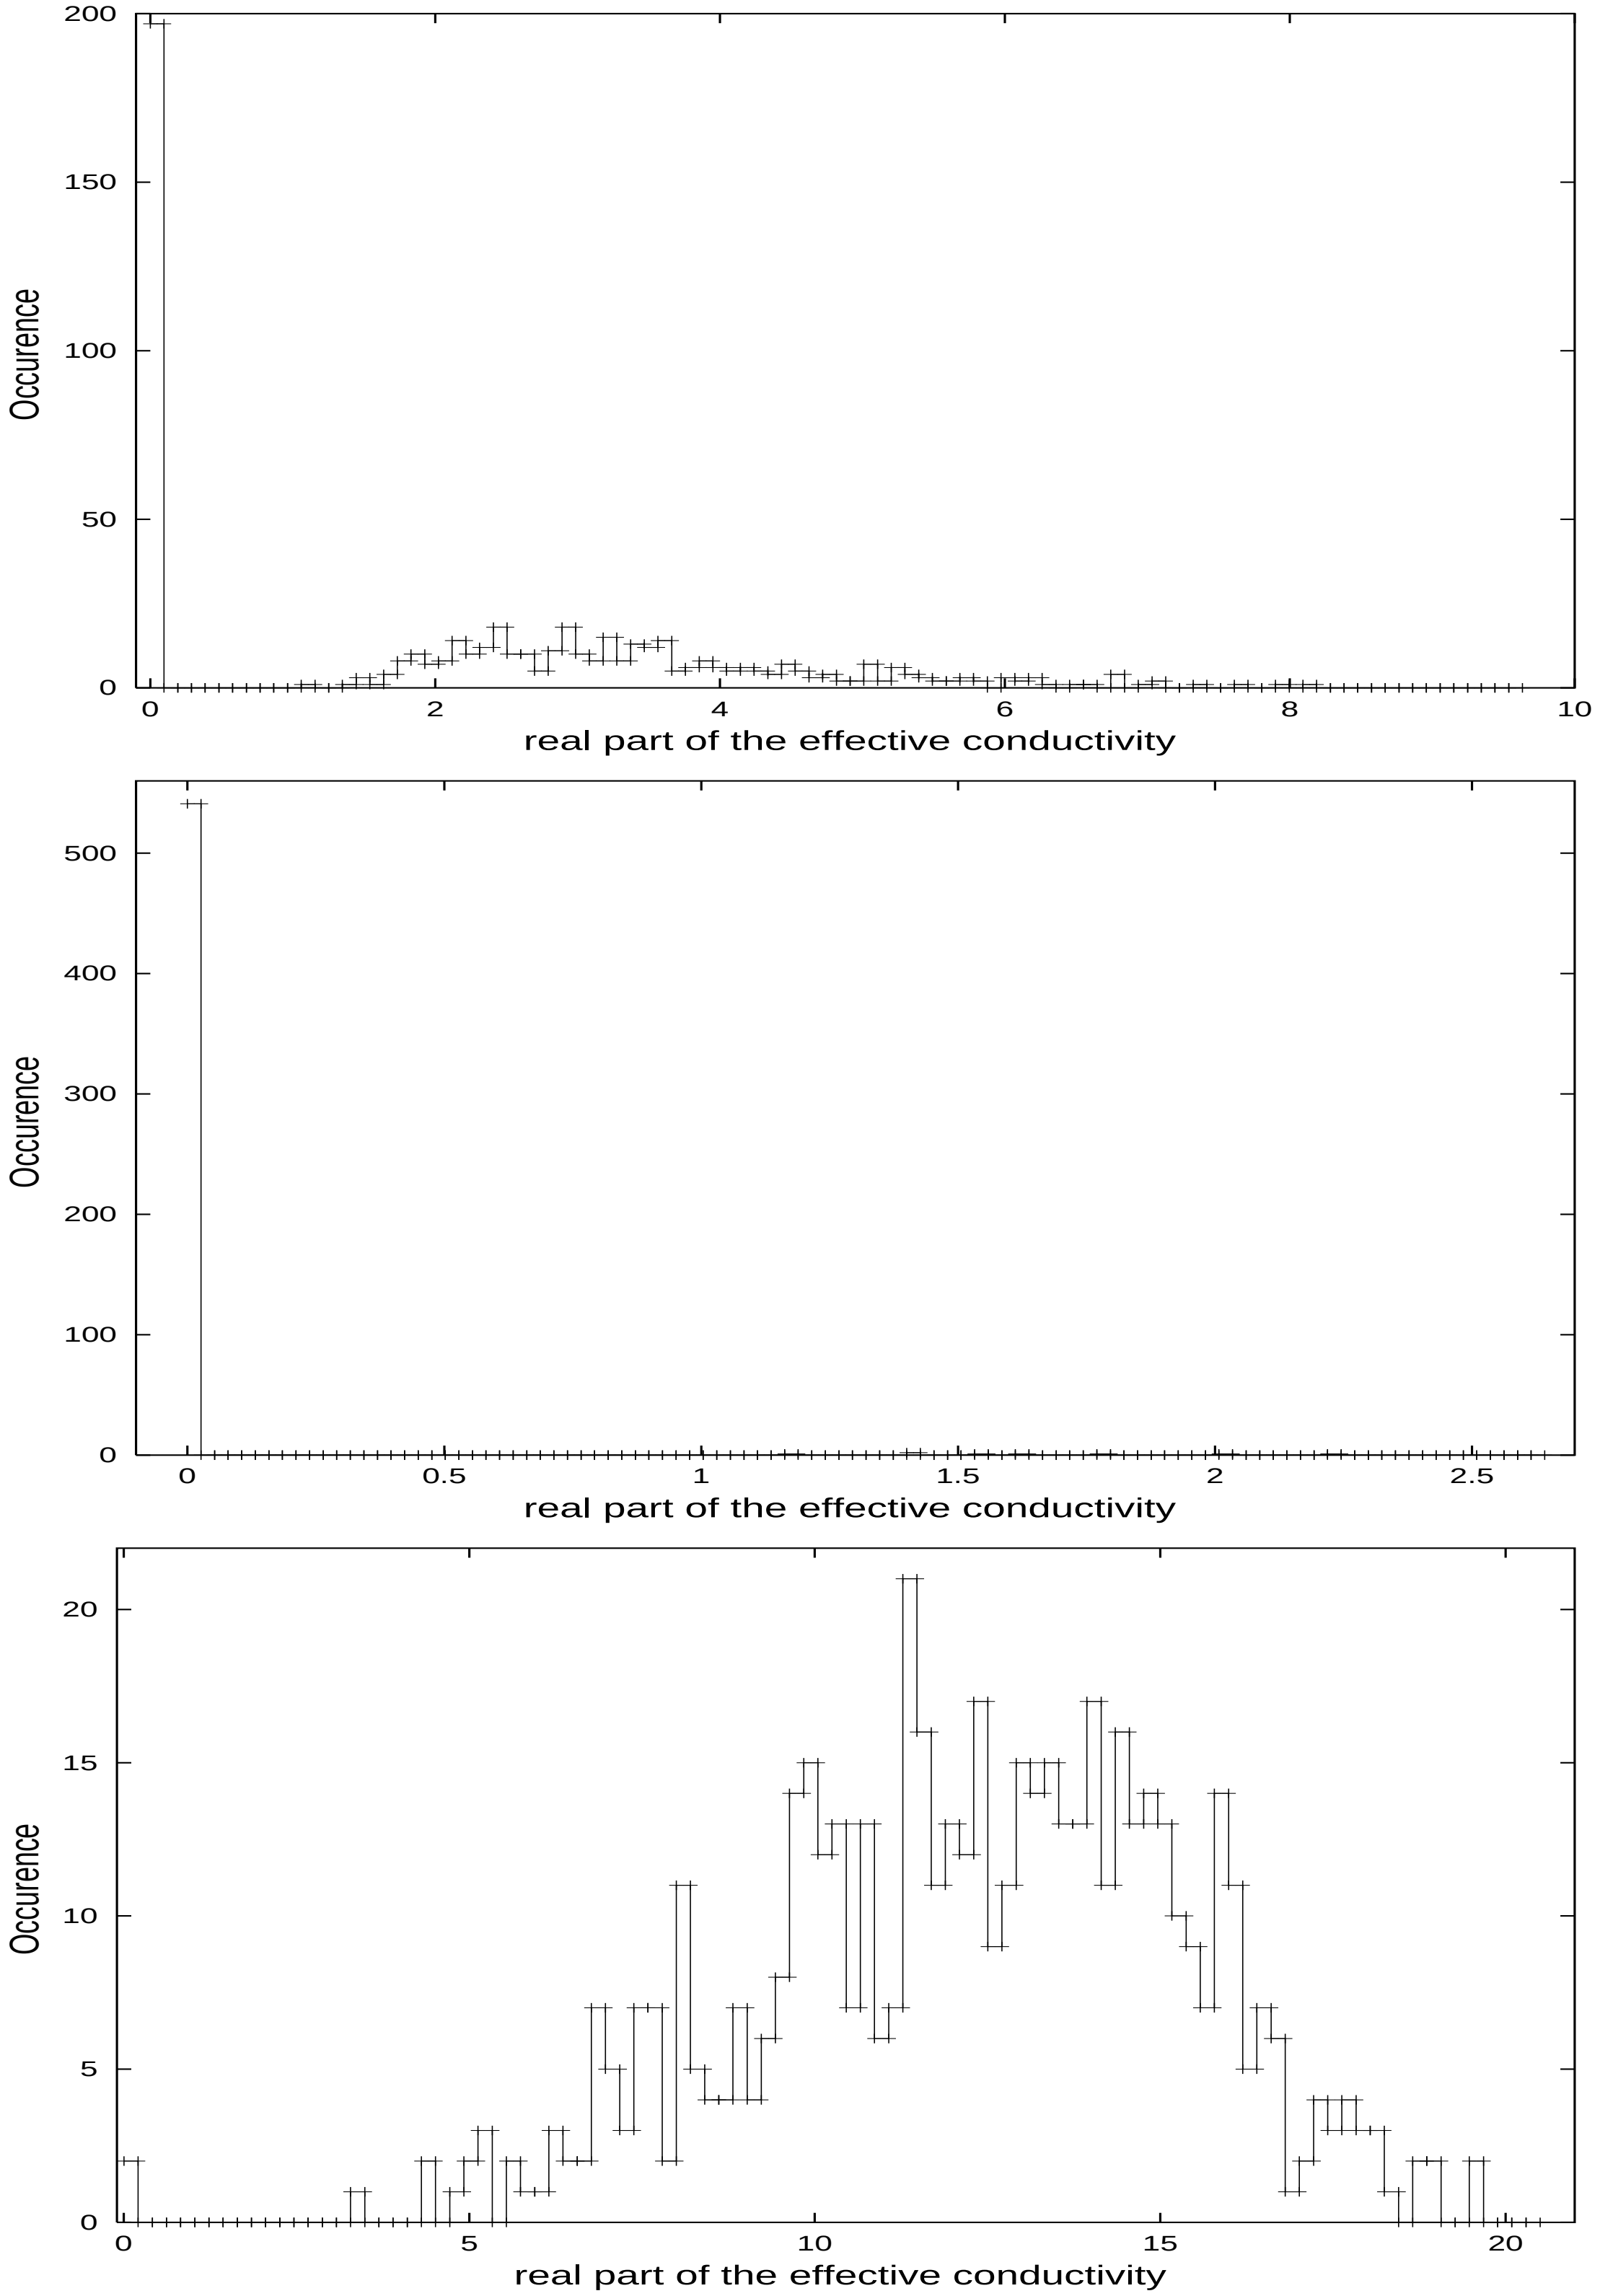

Figure 2: Distribution of the real part of the effective conductivity expressed in arbitrary units, using RL model and AA over 550 samples of size 200 at frequency $\tilde{\omega} = 10^{-3}$, at p_c (a), below p_c (b) and above p_c (c)

References

[1] Landauer R., in *Electrical Transport and Optical Properties of Inhomogeneous Media (Ohio State University)*, Proceeding of the first conference on the Electrical Transport and Optical Properties of Inhomogeneous Media, AIP Conf. Proc. No. 40, edited by Garland J. C. and Tanner D. B. 1978 (AIP, New York).

[2] Bergman D J and Stroud D 1992 *Solid state Physics* **46** 147. Clerc J P, Giraud G, Laugier J M and Luck J M, 1990 *Adv. Phys.* **39**, 191.

[3] Stauffer D. and Aharony A., *Introduction to Percolation Theory, 2nd Ed. (Taylor and* Francis, London, 1994).

[4] Dykhne A M 1970 *Zh.Eksp. Teor. Fiz.* **59**, 110(Engl.Transl.1971 *Sov. Phys.-JETP* **32**348). Bruggeman D A 1935 *Ann. Phys.,Leipzig.* **24** 636.

[5] Landauer R 1952 *J. Appl. Phys.* **23**, 779

[6] Zeng X. C., Hui P. M. and Stroud D. 1989 *Phys. Rev B* **39**, 1063.

[7] Koss R. S. and Stroud D. 1987 *Phys. Rev B* **35**, 9004.

[8] Waston B. P. and Leath P. 1974 *Phys. Rev B* **9**, 4893.

[9] Cummings K. D., Garland J. C. and Tanner D. B. 1984 *Phys. Rev B* **30**, 4170.

[10] Brouers F., Sarychev A. K., Blacher S. and Lothaire O. 1997 *Physica. A* **241**, 146.

[11] Zekri L, Zekri N, Bouamrane R and Brouers F 2000 *J. Phys.:Condens. Matt.* **12** 293.

[12] Lobb C. J. and Frank D. J. 1984 *Phys. Rev B* **30**, 4090; Frank D. J. and Lobb C. J. 1988 *Phys. Rev B* **37**, 302.

[13] Zekri L, Bouamrane R and Zekri N 2000 *J.Phys.A:Math.Gen.* **33** 649.

[14] Kreibig U and Vollmer M, *Optical Properties of Metal Clusters* (Springer-Verlag, Berlin, 1995). Wooten F, *Optical Properties of Solids* (Academic, New York, 1972)

[15] Clerc J P, Zekri L and Zekri N submitted to *Phys. Lett. A*

[16] Berhier S, *Optique des milieux composites* 1993 Polytechnica, Paris